


POLTRACK JOGGING TRACK SBR SYSTEM

Total thickness 12mm

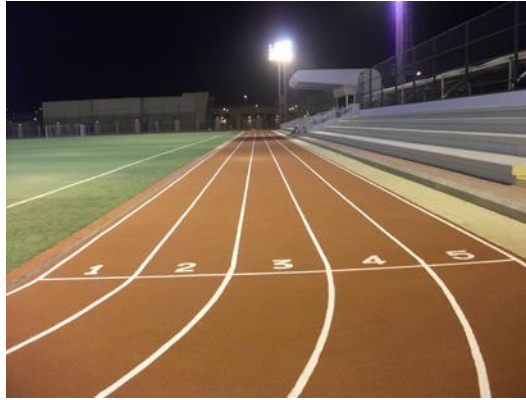

Elastic, seamless, flexible colored flooring, ideal for jogging tracks in total thickness of 12mm.

It consists of a shock-pad base of **PU BINDER 1118** with **RECYCLED RUBBER 858**. Follows the PU self-leveling coating, **POLYSPORT PU 1051** with **EPDM DUST** as a sealing layer and finally the PU, UV-resistant aliphatic top layer, **POLYSPORT 1052**, in two crossing layers.

The success of the application depends on the right preparation of the underlay and use of the material.

Steps:

1. PU PRIMER 870 - Polyurethane primer.

Applied by brush, roller or spray.

2. Mixture of PU BINDER 1118 and RECYCLED RUBBER 858 (in granulometry of 0.5-2mm) applied by paving machine.

3. Mixture of POLYSPORT PU 1051 and EPDM dust as a sealing layer for filling the porous of the prefabricated subfloor of sports floorings such as ISOPOL 854 or wet-pour cushion shock-pads. Applied by flat trowel.

4. POLYSPORT 1052 - UV-resistant, polyurethane, two-component, top coating for outdoor sports floorings.

Applied in two crossing layers, by airless spray or rollers.

Substrate

Asphalt is the safer subfloor for sport floorings for sure and must be always preferred than concrete surfaces.


A. Asphalt Substrate

The asphalt must have a slope of 0.7-1% and must dry for at least 30 days so that all solvents from the asphalt can evaporate.

The asphalt sub-floor should be applied on well compacted 150mm road base sub-floor and asphalt should be laid in one layer (and not 2) in 6 to 8cm with fine and coarse aggregates (up to 15mm granulometry) like the kind of asphalt used in road construction.

So, new road-grade asphalt will have to be laid (minimum 60mm) in one layer containing coarse aggregates and then mature for 30 days at least, before any application takes place on top of the asphalt to avoid bubbles on the final layer of the sport or rubber floorings.

Asphalt Infrastructure

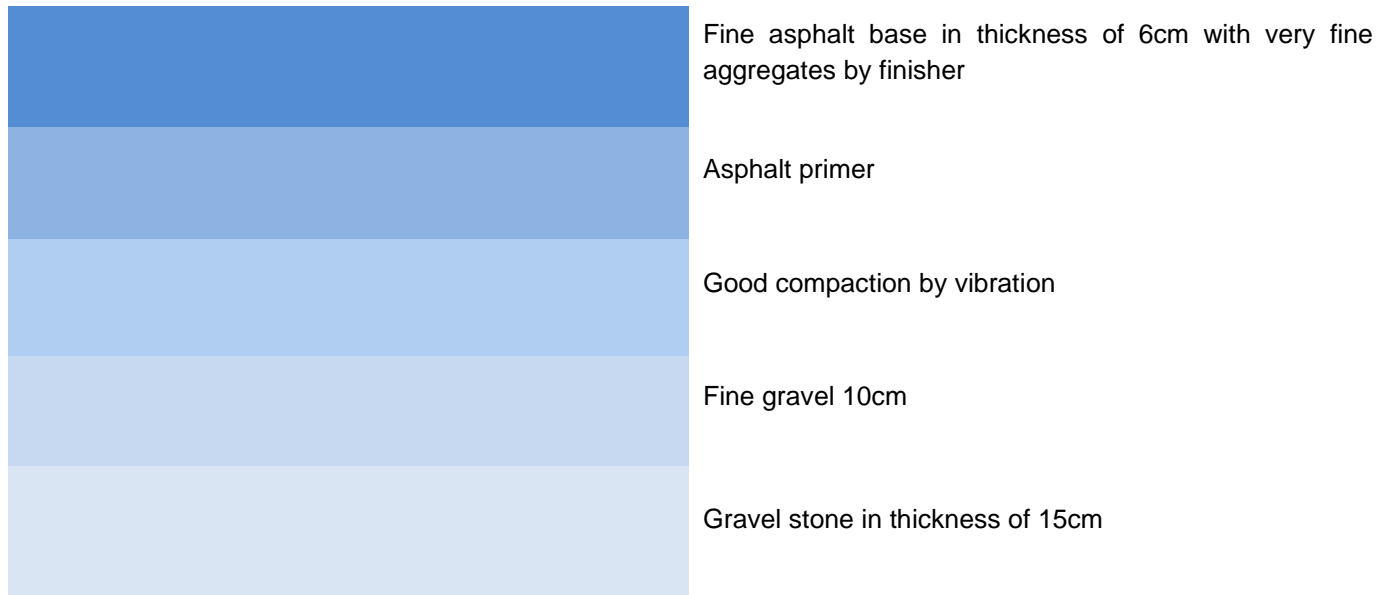


B. Concrete Surface

Concrete surface must be power-trowelled without cracks and must be smooth with a slope of 0.7-1% and humidity under 4% in 10cm depth of concrete.

Concrete must also be **dry at least for 40 days** and then the application takes place if there is no rising humidity for the sub-floor. Before the application takes place, there must be proper grinding of the surface by a grinding machine to open the pores accordingly and also a measurement by special instrument to measure humidity on the surface and in 10cm under the surface.

Generally concrete is a risky sub-floor and there may be problems with rising humidity, especially in areas where the sea level is really high and when the sea is close or in areas near greenery.

Always make expansion joints in large areas of concrete, to avoid uncontrollable cracks and failures. Joints should be every 25 square meters creating a grid of 5x5 meters or close to that.

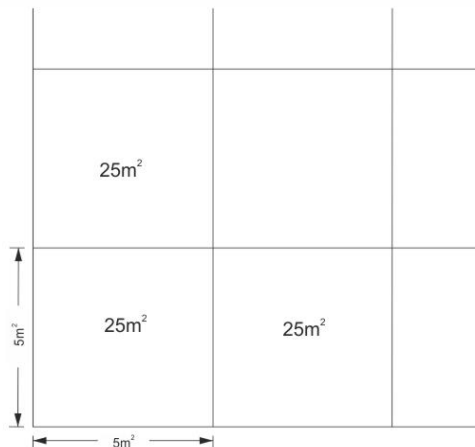

Substrate requirements

Concrete quality	at least C20/25
Age:	at least 40 days
Moisture content:	below 4%

KDF - Kataskeves Dapedon LTD
e : exports@kdf.gr w : www.kdf.gr

Showroom Office
19th km National Road Thessaloniki-Moudania
57001, Neo Rysio, Thessaloniki, Greece
t / f : +30 2310 829598

Accounting Office
19 Mitropoleos Str
54624, Thessaloniki, Greece



KDF

Sports Flooring Systems & Building Materials
50 YEARS OF EXPERIENCE

Tools:



airless sprayer



brush



brush



paving machine



flat trowel



V-notch trowel



sandpaper machine



roller

KDF - Kataskeves Dapedon LTD
e : exports@kdf.gr w : www.kdf.gr

Showroom Office
19th km National Road Thessaloniki-Moudania
57001, Neo Rysio, Thessaloniki, Greece
t / f : +30 2310 829598

Accounting Office
19 Mitropoleos Str
54624, Thessaloniki, Greece

